


 Cite this: *RSC Adv.*, 2022, 12, 18794

Photocatalytic dye-degradation activity of nano-crystalline $\text{Ti}_{1-x}\text{M}_x\text{O}_{2-\delta}$ ($\text{M} = \text{Ag}, \text{Pd}, \text{Fe}, \text{Ni}$ and $x = 0, 0.01$) for water pollution abatement

 Vaishali Soni,^a Abhay Narayan Singh,^b Preetam Singh^c and Asha Gupta^{*a}

Nanocrystalline metal-ion ($\text{M} = \text{Fe}, \text{Ni}, \text{Ag},$ and Pd) doped and undoped anatase- TiO_2 powders were prepared using a solution combustion method. The photocatalytic degradation of different dyes such as methylene blue (MB), rhodamine B (RB), rhodamine B base (RBB), and thionine acetate (TA) was investigated under UV exposure. The degradation rate of the dyes were found to be better in the case of Ag^+ and Pd^{2+} doped TiO_2 , whereas Fe^{3+} and Ni^{2+} doped TiO_2 showed lower photocatalytic activity compared to undoped TiO_2 nanoparticles. Combustion synthesized catalysts exhibited much better activity compared to the commercial Degussa P25 (75% anatase + 25% rutile) TiO_2 photocatalyst. The intermediate states created in the band gap of the TiO_2 photocatalyst due to doping of first row transition metal ions (such as Fe^{3+} and Ni^{2+}) into the TiO_2 lattice act as recombination centres and the electrons present in the d-orbital quench the photogenerated holes by indirect recombination, hence increasing $e^- - h^+$ recombination rates. As a result, a decrease in the photocatalytic activity of TiO_2 doped with first row transition metal ions is observed. However, in the case of noble metal ions (such as Ag^+ and Pd^{2+}) in TiO_2 , photoreduction of Ag^+ and Pd^{2+} ions occurs upon UV irradiation, hence the noble metal-ions act as electron scavengers. Consequently, the lifetime of the holes (h^+) increases and hence higher photocatalytic oxidation activity of the dyes is observed. A novel strategy of electron scavenging is envisaged here to develop Ag^+ and Pd^{2+} doped TiO_2 to increase the photocatalytic oxidation of organic dyes for the development of better water pollution abatement catalysts. Redox-pair stabilization in the TiO_2 lattice similar to photo-chromic glasses play a defining role in enhancing the photocatalytic activity of the catalyst and is a key finding for the development of superior photocatalysts. With the help of UV-vis and fluorescence spectroscopy, the mechanisms of the superior oxidation activity of Pd^{2+} and Ag^+ doped TiO_2 nanoparticles are explained.

 Received 5th May 2022
 Accepted 30th May 2022

DOI: 10.1039/d2ra02847f

rsc.li/rsc-advances

1. Introduction

Semiconductor heterogeneous photocatalysis is a promising strategy with enormous potential to treat contaminants in water to remove persistent organic pollutants as well as microorganisms in water. The discharge of highly toxic and potentially carcinogenic dyes from textile industries are the root cause of water pollution and therefore poses a serious environmental concern; about 10–15% of the total dyes are wasted during dyeing and released as effluents into wastewater streams.¹ Several studies have been carried out regarding complete degradation of organic dyes using semiconductors as photocatalysts before releasing them into water streams.^{2,3} Complete

degradation and mineralization of organic pollutants in water have been extensively explored in the literature.^{4–9} In recent years, photocatalytic reactions over semiconductor oxides have been investigated in depth.^{10–12} Although other semiconductors, such as ZnO ,¹³ ZnS ,¹⁴ Fe_2O_3 ,¹⁵ WO_3 ,¹⁶ Nb_2O_5 ,¹⁷ Ta_2O_5 ,¹⁸ CdS ,¹⁹ In_2O_3 ,²⁰ *etc.*, have been studied extensively, TiO_2 remains the leading and most studied photocatalytic material due to its photostability, low cost, redox efficiency, and non-toxicity towards the environment and humans.^{7,10,11} Several studies in the literature have reported that the anatase phase of TiO_2 is more photo-active for degrading pollutants in contaminated water compared to the other stable polymorphic rutile and brookite phases.^{10,11,21,22}

The band gap of TiO_2 is such that photo-absorption occurs in the UV region of the electromagnetic spectrum and, therefore, successful attempts have been made to shift the band gap of TiO_2 towards the visible or near UV region by doping of foreign elements, especially transition metal ions, into the TiO_2 lattice or loading them onto the TiO_2 surface.^{23–26} However, several controversies regarding metal substitution in catalysts prevail

^aDepartment of Chemistry, Indian Institute of Technology (BHU), Varanasi-221005, India. E-mail: asha.chy@itbhu.ac.in; toashagupta@gmail.com; Tel: +91 6390363140

^bSchool of Materials Science and Technology, Indian Institute of Technology (BHU), Varanasi-221005, India

^cDepartment of Ceramic Engineering, Indian Institute of Technology (BHU), Varanasi-221005, India


in the current literature. Some of the literature has reported that the photo-activity of titania is altered by doping with transition metals like Pt, Pd, Au, Ag, and Cu,^{27–31} which act as charge separators for the photo-induced electron-hole pair. It is hypothesized that after excitation, the electron migrates to the metal centre, where it becomes trapped and electron-hole recombination is suppressed, which results in enhanced photo-activity. Nagaveni *et al.*^{32,33} conducted a systematic study of several metal ions such as Cu²⁺, Fe³⁺, Zr⁴⁺, Ce⁴⁺, and V⁵⁺ and reported that substitution of these metal ions in TiO₂ decrease the photocatalytic activity. The formation of reactive oxygen species (*viz.* OH[•], O₂^{•-}, and H₂O₂) during catalytic processes on metal oxide semiconductors are of paramount importance for the practical application of photocatalysis. However, trapping of either e⁻ or h⁺ by the new energy band in the metal doped TiO₂ matrix decreases the number of these reactive oxygen species, resulting in a decreased photocatalytic activity.³²


Electron scavenging through photo-reduction of metal-ions similar to the phenomena occurring in photo-chromic glasses can act as an alternative way to enhance the photocatalytic activity of doped TiO₂. In photochromic glasses, reversible photo-reduction of Ag⁺ to Ag⁰ occurs to attain photochromism where the photoelectron is being trapped *via* Ag⁺ ion reduction giving a dark colour to the glasses and once photon irradiation is stopped, Ag transforms back to the Ag⁺ state. Thus, we have introduced Ag⁺ and Pd²⁺ ions into the TiO₂ lattice to attain reversible photo-reduction or scavenging of photoelectrons to enhance the photocatalytic oxidation activity of Ag⁺ and Pd²⁺ doped TiO₂ with enhancing of the lifespan of the holes (h⁺). There are a variety of approaches that are used to synthesize anatase-TiO₂ NPs, such as the sol-gel process,^{34,35} hydrothermal method,³⁶ microemulsion technique,^{37,38} inert gas condensation,³⁹ chemical vapour deposition,⁴⁰ *etc.*, but solution combustion provides a rapid, self-propagating, single-step synthesis approach yielding nanoscale materials. Most of the metal doped TiO₂ reported in the literature is prepared by the two most common methods: incipient wet impregnation⁴¹ and co-precipitation techniques.²³ However, in the impregnation method, doping is likely to occur only on the surfaces, while in the co-precipitation method, the long-time heat treatment of these mixed metal hydroxides leads to agglomeration of metal particles at the surface of TiO₂. Therefore, a new method for the preparation of metal ion doped titania is essential to study the effect of the metal ion in the TiO₂ lattice. The solution combustion method offers a versatile and simple approach for *in situ* doping of metal ions in oxide materials. In the solution combustion method, highly crystalline fine particles are obtained and have the advantage of controlling the stoichiometric amount of doping of desired metal ions in TiO₂.^{32,33,42,43}

In this work, we present the one step synthesis of nanocrystalline Ti_{1-x}M_xO_{2-δ} (M = Fe, Ni, Ag and Pd; x = 0, 0.01) by a solution combustion method and the photocatalytic degradation of different dyes such as methylene blue (MB), rhodamine B (RB), rhodamine B base (RBB), and thionin acetate (TA) were investigated using the developed photocatalyst, Ti_{1-x}M_xO_{2-δ} under UV light exposure.

2. Experimental section

2.1 Synthesis

TiO₂ nanoparticles (NPs) were obtained by a solution combustion method using the precursor titanium nitrate [TiO(NO₃)₂] and glycine (NH₂CH₂COOH, 99%) as a fuel. 5 ml of titanium-isopropoxide ([Ti(OC₃H₇)₄], 97%) in 15 ml of isopropanol (99%) was subjected to hydrolysis to obtain the white precipitate of titanium hydroxide [TiO(OH)₂], which was further reacted with 1 ml of 69 wt% nitric acid in ice cold conditions to obtain *in situ* titanium nitrate [TiO(NO₃)₂] solution. 1.4 g of glycine was added to titanium nitrate solution and the reaction mixture was kept in a pre-heated furnace at 400 °C. All the chemicals were obtained in their highest purity form from Sigma-Aldrich. For the synthesis of 1 atom% Pd doped TiO₂, for instance, titanium nitrate, PdCl₂ and glycine were taken in a molar ratio of 0.99 : 0.01 : 1.14. The combustion reaction can be represented as:



The product was light brown in colour. Similarly, AgNO₃, Fe(NO₃)₃ and Ni(NO₃)₂ were used as the precursor compounds for the synthesis of the 1 atom% Ag, Fe, and Ni doped titania, and their colour was light yellow, light brown, and yellow, respectively.

2.2 Characterization of Ti_{1-x}M_xO_{2-δ} (M = Ag, Pd, Fe, and Ni and x = 0, 0.01)

To confirm the phase formation of the synthesized photocatalysts, powder X-ray diffraction (pXRD) spectra were obtained from a Philips X'pert Pro Diffractometer with Cu Kα radiation in the 2θ range from 20 to 70° with step size 0.02° at a scan rate of 1° min⁻¹ for the purpose of Rietveld refinement. The SEM images of the powder sample were carried out using a high resolution-scanning electron microscope (FEI Nova Nano SEM450) and TEM micrographs of sample were obtained with a high resolution-transmission electron microscope (FEI TECNAI G2 20 TWIN instrument operated at 200 kV). The X-ray photoelectron spectroscopy (XPS) measurements were performed on a VG Scientific ESCA Lab Mark II spectrometer (UK) with an aluminium anode source producing Al Kα radiation (1486.6 eV). UV-vis DRS spectra of the doped and undoped TiO₂ powders were obtained using a PerkinElmer Lambda 35 spectrophotometer in the wavelength range of 200 to 800 nm. Each sample was dry-pressed into a 10 mm diameter round disk containing 250 mg of the powder samples; pure BaSO₄ was used as a standard for referencing. The photoluminescence measurements were performed on a luminescence spectrophotometer (PerkinElmer LS 55) at room temperature.

2.3 Photocatalytic studies

The photocatalytic activity of the synthesized nano-sized catalysts were measured by degrading MB, RB, RBB, and TA under



UV-vis light illumination. The experiments were carried out using an annular-type cylindrical batch photo-reactor (of 250 ml volume) consisting of a jacketed quartz tube of 1.4-inch inner diameter, 1.6 inch outer diameter, and 8.3 inch length. The outer shell of a high-pressure mercury vapour lamp of 125 W (Philips Powertone, Mumbai, India) was removed carefully and placed inside the quartz reactor. The ballast and capacitor were connected in series to avoid fluctuations in the input power supply of the lamp, and a constant water supply was maintained to avoid overheating during the reaction. The whole unit was placed inside a glass container filled with polluted/dyed-water solution. The distance between the source and bottom of the vessel was maintained at 0.8 inch to stir the solution. The lamp was irradiated predominantly at 365 nm (3.4 eV). The dye concentration employed was 100 ppm with a catalyst loading of 1 kg m^{-3} and 1 ml of dye solution was collected at a regular interval of 5 minutes for further analysis by the spectrophotometer.

2.4 Sample analysis

The degraded samples were filtered through Millipore membrane filters and centrifuged to remove the catalyst particles prior to analysis. The centrifuged sample is used to record the UV-vis spectra in the range 200–800 nm at a scan rate of 120 nm min^{-1} . The absorption maxima values for MB, RB, RBB, and TA are 664.8 nm, 553.6 nm, 553.60 nm, and 599.14 nm, respectively. The C/C_0 values are plotted against time (min) to obtain the degradation plot of each of the respective dyes.

3. Structural analysis of the catalyst

3.1 XRD studies

The powder diffraction patterns for $\text{Ti}_{1-x}\text{M}_x\text{O}_{2-\delta}$ ($\text{M} = \text{Fe}, \text{Ni}, \text{Ag}$, and Pd ; $x = 0, 0.01$) shown in Fig. 1 are indexed to the anatase phase only; diffraction peaks corresponding to the rutile and brookite polymorphic phases could not be identified. Further, we have refined X-ray data to obtain the structural parameters. The Rietveld refinement of the X-ray spectra of TiO_2 , Ag^+ doped TiO_2 and Pd^{2+} doped TiO_2 has been done taking pseudo-Voigt as the peak profile function, as depicted in Fig. 2(a)–(c), respectively. The experimental, calculated and their difference patterns were denoted as a solid, dotted and continuous bottom line, respectively. The position of the Bragg reflections represented by the tick marks corresponds to the tetragonal structure of anatase TiO_2 . From the Rietveld refinement, the values of the lattice parameters (a , b , and c), unit cell volume (V), and reliability factors (R_{Bragg} , R_f and χ^2) for combustion synthesized doped and pure TiO_2 are listed in Table 1. Incorporation of Ag/Pd ions in the TiO_2 lattice have very little impact on the lattice parameter and a slight distortion in the lattice parameter is observed upon Ag/Pd ions substitution, as shown in Table 1. The crystallite size was determined using the Scherrer formula and from the FWHM of the highest intensity peak (101), it was found to be in the range of 8–18 nm for metal doped titania.

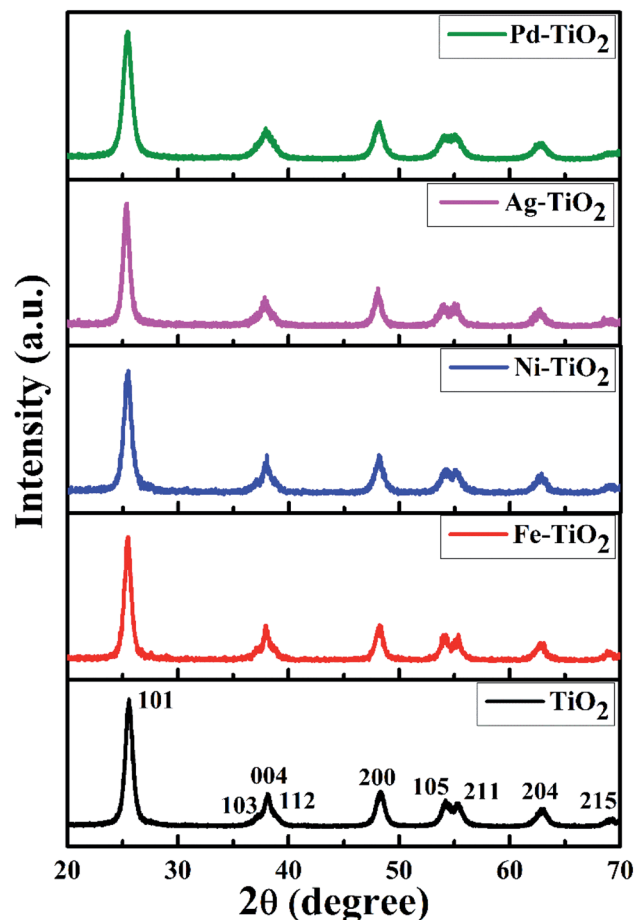


Fig. 1 XRD patterns of TiO_2 and $\text{Ti}_{1-x}\text{M}_x\text{O}_{2-\delta}$ ($\text{M} = \text{Fe}, \text{Ni}, \text{Ag}$, and Pd ; $x = 0, 0.01$).

3.2 SEM and TEM studies

The surface morphology and structural characteristics were investigated by SEM micrographs. The SEM image of Ag^+ doped TiO_2 NPs, as shown in Fig. 3(a), shows the presence of a porous, sponge-like structure with high roughness and complexity. The bright-field TEM image, Fig. 3(b), of Ag^+ doped titania shows agglomerated nanoparticles of sizes ranging from 10 to 20 nm, in close agreement with the sizes obtained from the Scherrer formula. The high resolution-TEM image, Fig. 3(c), displays lattice fringes with an interplanar d -spacing of 0.35 nm corresponding to the (101) plane of anatase- TiO_2 , which is in accordance with the pXRD results. The presence of distinct rings in the selected area electron diffraction (SAED) pattern, as shown in Fig. 3(d), indicate that the combustion synthesized doped TiO_2 powders are crystalline in nature and could be indexed to the anatase phase only.

3.3 XPS

The deconvoluted X-ray photoelectron spectra (XPS) of the combustion synthesized Pd^{2+} doped TiO_2 are shown in Fig. 4. The binding energies reported here are with reference to the adventitious C 1s peak (284.8 eV). Fig. 4(a) represents the Ti 2p



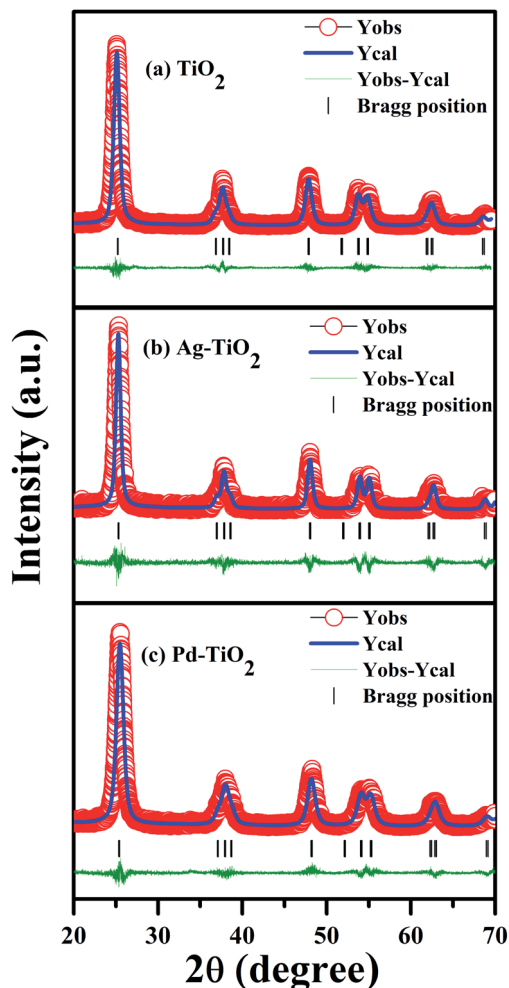


Fig. 2 Rietveld refined XRD patterns of (a) TiO_2 , (b) Ag-TiO_2 , and (c) Pd-TiO_2 .

core level spectra which indicates two peaks centered at 458.8 and 465.0 eV corresponding to Ti $2p_{3/2}$ and Ti $2p_{1/2}$ levels (Ti^{4+}), respectively.⁴⁴ Fig. 4(b) represents the Pd 3d core level spectra of Pd^{2+} doped TiO_2 which consists of two peaks centered at 338.0 and 343.7 eV corresponding to Pd $3d_{5/2}$ and Pd $3d_{3/2}$ which confirms that Pd is present in the +2 oxidation state.^{44,45} When the powder sample (Pd^{2+} doped TiO_2) was exposed to UV light, the peaks corresponding to Pd $3d_{5/2}$ and Pd $3d_{3/2}$ asymmetrically broaden, as shown in Fig. 4(c), which indicates that Pd is present in its two chemical states *i.e.*, Pd^0 and Pd^{2+} . The additional peaks that start growing at 336.0 and 341.7 eV indicate the formation of metallic Pd^0 . These two peaks are deconvoluted to obtain the fractional analysis of Pd^0 and Pd^{2+} in irradiated Pd^{2+} doped TiO_2 and the ratio observed between Pd^{2+} to Pd^0 was approximately 0.7 to 0.3. Further, darkening of the powder sample upon irradiation, as shown in the inset of Fig. 4(b) and (c), also confirms the formation of the Pd^0 state at the expense of the Pd^{2+} state indicating a similar phenomenon of photochromism observed in Pd^{2+} doped TiO_2 sample.

Table 1 Structural parameters of combustion synthesized pure TiO_2 , Ag-TiO_2 , and Pd-TiO_2

Compound	TiO_2	$\text{Ag}_{0.01}\text{Ti}_{0.99}\text{O}_2$	$\text{Pd}_{0.01}\text{Ti}_{0.99}\text{O}_2$
a (Å)	3.8012(2)	3.7882(10)	3.77627(12)
b (Å)	3.8012(2)	3.7882(10)	3.77627(12)
c (Å)	9.5386(5)	9.514(2)	3.8012(2)
V (Å) ³	137.8244	136.53	135.3024
Ti/Ag/Pd (4c)			
X	0	0	0
Y	0.25	0.25	0.25
Z	0.375	0.375	0.375
O (4b)			
X	0.00	0.00	0.00
Y	0.25	0.25	0.25
Z	0.1657	0.1668	0.1663
Reliability factor of goodness of fit			
χ^2	1.17	1.38	1.25
R_F	1.33	4.22	1.63
R_{Bragg}	1.53	6.70	2.27
R_p	8.99	20.7	10.3
R_{wp}	12.9	27.8	13.8

3.4 The Kubelka–Munk plot of metal doped TiO_2

In order to study the optical bandgap of the sample, diffuse reflectance measurements were carried out through UV-vis spectroscopy. The Kubelka–Munk (K–M) function was used to convert the reflectance spectra, thus obtained, into an equivalent absorption spectrum. The optical band gaps of the prepared materials were calculated from the linear part of the energy dependence of the absorption spectra using the following equation:

$$F(R) = \frac{(1-R)^2}{2R}$$

$$(F(R)h\nu)^{1/2} = A(h\nu - E_g)$$

where $h\nu$ is the energy of the photon and $F(R)$ denotes the Kubelka–Munk function and the graph plotted between $(F(R)h\nu)^{1/2}$ vs. $h\nu$ gives the optical energy-band gap of the powder sample.

The band-gap of the synthesized pale yellow TiO_2 NPs was found to be 2.94 eV (426 nm), as shown in Fig. 5(a), which is quite lower than that of Degussa-P25 TiO_2 (3.10 eV).⁴⁶ This decrease is attributed to the presence of interstitial carbide ions in the TiO_2 lattice.^{33,43} While in the case of Fe^{3+} , Ni^{2+} , Ag^+ , and Pd^{2+} doped TiO_2 , the energy band-gap values were found to be 2.83 (440 nm), 2.69 eV (463 nm), 2.78 (447 nm), and 2.85 eV (435 nm), respectively, as shown in Fig. 5(b)–(e). It was observed that doping of the metal ion in the TiO_2 lattice causes a significant red shift of absorption threshold in the visible region; even 1 atom% doping concentration brought about noteworthy changes in the colour of the otherwise pale yellow TiO_2 NPs. The origin of the visible spectra in the case of the metal doped



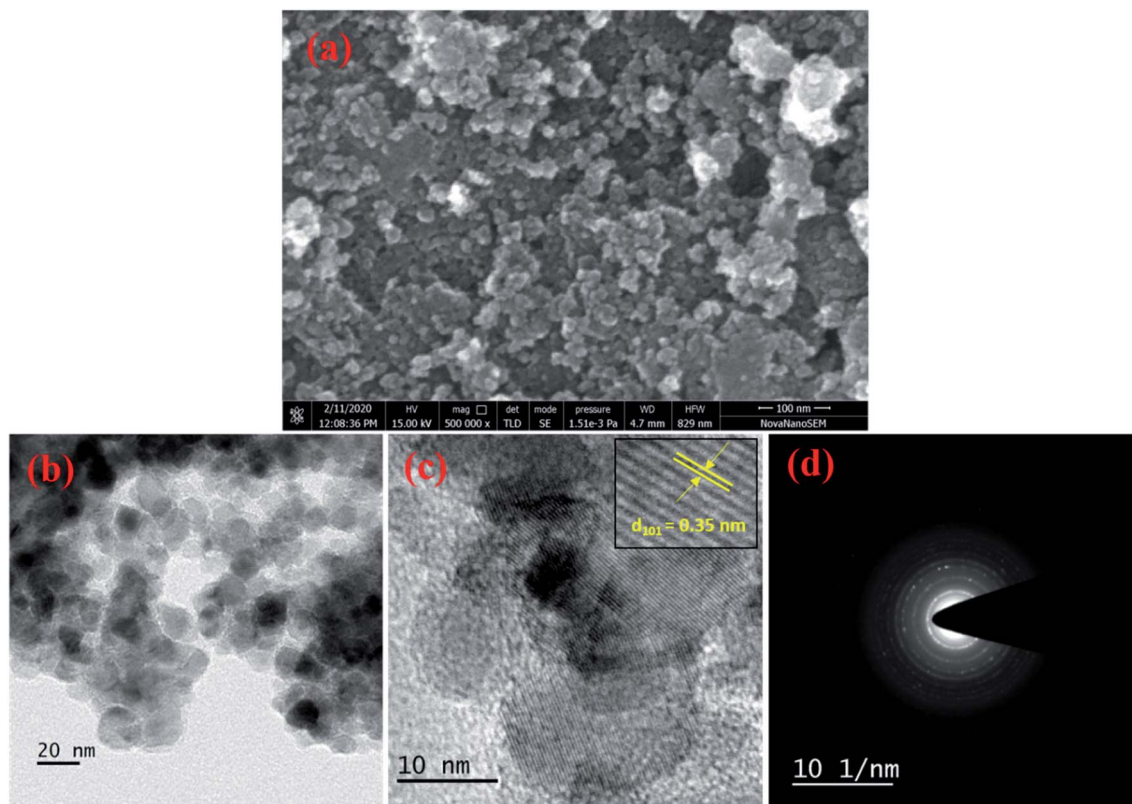


Fig. 3 (a) SEM micrographs, (b) bright field TEM image, (c) HR-TEM with interplanar d -spacing, and (d) SAED pattern of Ag-TiO₂.

sample is due to the formation of additional dopant energy level, which results in the electronic transitions from the valence band to the dopant level or from the dopant level to the conduction band of TiO₂. Fe³⁺ and Ni²⁺ doped TiO₂ shows similar absorption behaviour as that of TiO₂ and the observed red shift is due to the transition from the metal (3d) level to the conduction band edge of TiO₂ NPs. In the case of Ag⁺ and Pd²⁺ doped TiO₂, a broad hump around 2.25 eV (550 nm) and 2.48 eV (500 nm) was also observed due to surface plasmon absorption of Ag⁺ and Pd²⁺ ions, respectively. We believe that the plasmonic absorption occurs due the reduction of Ag⁺ and Pd²⁺ ions into their metallic state (such as Ag⁰ and Pd⁰) during the measurement of the UV spectrum. Further, we have applied the baseline approach to see the effect of the surface plasmon absorption on

the optical band gap of TiO₂ and the result is given in Table 2, which indicate that E_g values obtained from the baseline method are ~ 0.2 eV higher than the values obtained from the K-M plot, as shown as the inset of Fig. 5(d) and (e).⁴⁷ During irradiation, the colour of the catalysts turn black, indicating photo-reduction of Ag⁺ to Ag⁰ and Pd²⁺ to Pd⁰ and hence these ions act as electron scavengers that increase the lifespan of the photogenerated holes (h⁺), resulting in higher photo-oxidation activity. Thus, different d-electron configurations and the distributions of the dopant ions in the TiO₂ lattice can modulate the optical absorption and alter the energy band structures of the synthesized materials through different dopant-lattice interactions.³³

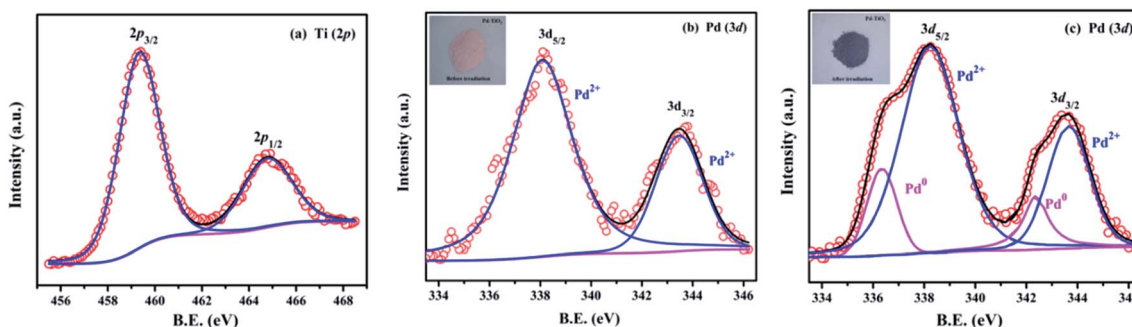


Fig. 4 (a) Ti (2p) core level spectra, and (b) and (c) Pd (3d) core level spectra of Pd²⁺ doped TiO₂ before and after UV irradiation, respectively.



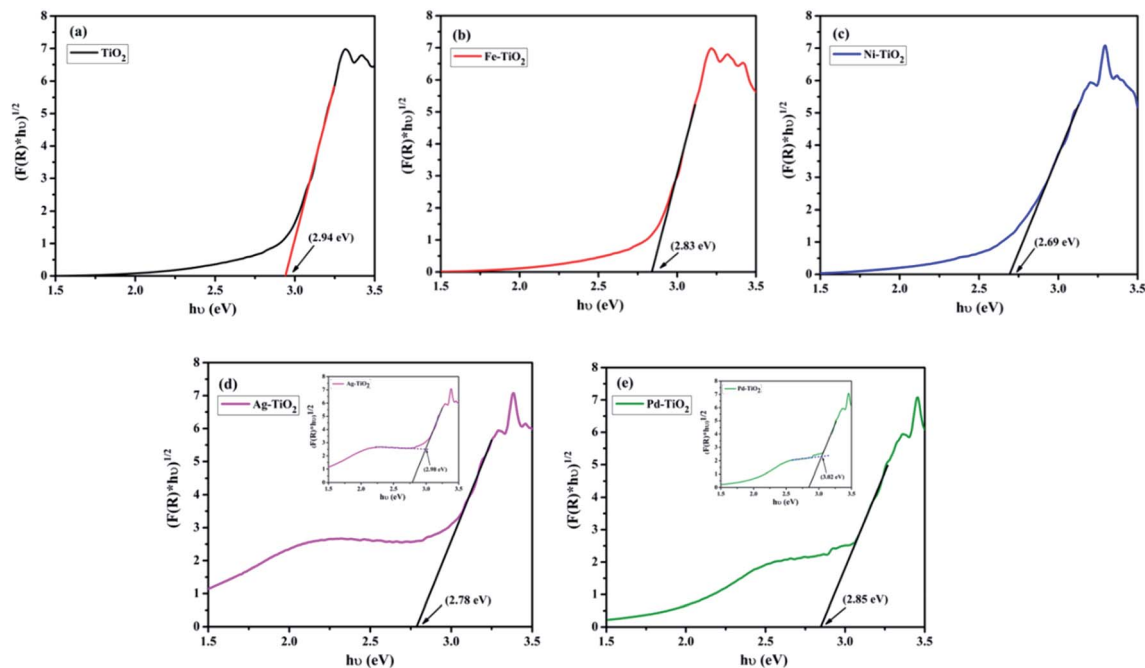


Fig. 5 (a)–(e) Kubelka–Munk plot of $\text{Ti}_{1-x}\text{M}_x\text{O}_{2-\delta}$ ($\text{M} = \text{Fe}, \text{Ni}, \text{Ag}, \text{and Pd}; x = 0, 0.01$). Insets of (d) and (e) represent the baseline approach for band gap estimation of Ag^+ and Pd^{2+} doped TiO_2 .

3.5 Photoluminescence of metal doped TiO_2

Fig. 6 represents the photoluminescence (PL) spectra for all the combustion synthesized pure and metal ion doped TiO_2 NPs. The PL spectra were recorded at an excitation wavelength of 290 nm which shows a broad band with multiple superimposed peaks nearly at $\sim 380, 415, 480,$ and 523 nm.^{48–53} The first emission peak around ~ 380 nm was observed for all the combustion synthesized TiO_2 photocatalysts which is attributed to direct recombination of the electron–hole which is larger than the forbidden gap (as TiO_2 is an indirect gap semiconductor).⁴⁸ The emission peak at ~ 415 nm is attributed to the indirect band gap partially allowed electronic transition,^{50–52} while the peaks at ~ 480 and 523 nm arise due to shallow trapped surface states such as $\text{Ti}^{4+}\text{-OH}$ or oxygen vacancies.^{50,53} It was noticed that upon metal ion doping the emission intensity decreases which indicates the lower recombination rate of the charge carriers. In the case of Fe^{3+} and Ni^{2+} doped TiO_2 , the decrease in the PL intensity can be attributed to the electron transfer from the conduction band of Ti^{4+} to the new levels introduced by partially filled 3d metal ions. The free hole can recombine with a trapped electron or a free electron can

recombine with a trapped hole. This electron–hole recombination may be non-radiative and transfer its energy to nearby ions and hence quench the fluorescence process. As a result, Fe^{3+} and Ni^{2+} doped TiO_2 exhibited lower photocatalytic activity than pure TiO_2 NPs. On the contrary, the Ag^+ and Pd^{2+} doped TiO_2 samples show the lowest intensity compared to other transition metal (Fe^{3+} and Ni^{2+}) doped TiO_2 , as shown in Fig. 6. These doped noble metal ions (Ag^+ and Pd^{2+}) trap the electron from the conduction band and prevent it from falling back down to the valence band. Thus, this decreased charge carrier

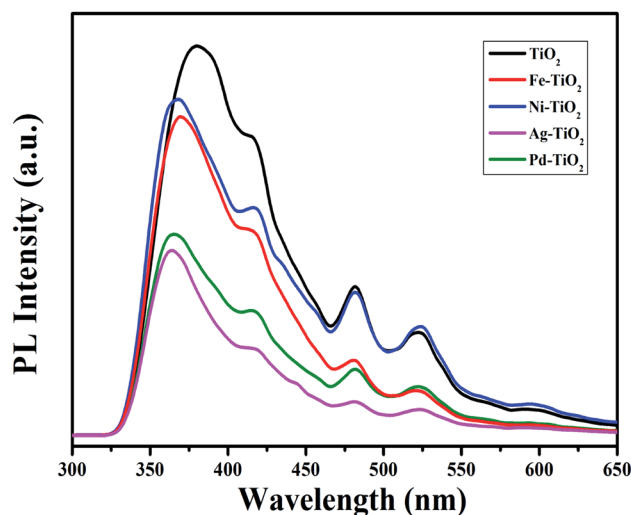


Fig. 6 Photoluminescence spectra of $\text{Ti}_{1-x}\text{M}_x\text{O}_{2-\delta}$ ($\text{M} = \text{Fe}, \text{Ni}, \text{Ag}, \text{and Pd}; x = 0, 0.01$).

Table 2 Experimental E_g values of Ag-TiO_2 and Pd-TiO_2 obtained by application of the K–M plot and baseline approach

Samples	Energy band gap (eV)	
	K–M method	Baseline method
Ag^+ doped TiO_2	2.78	2.98
Pd^{2+} doped TiO_2	2.85	3.02



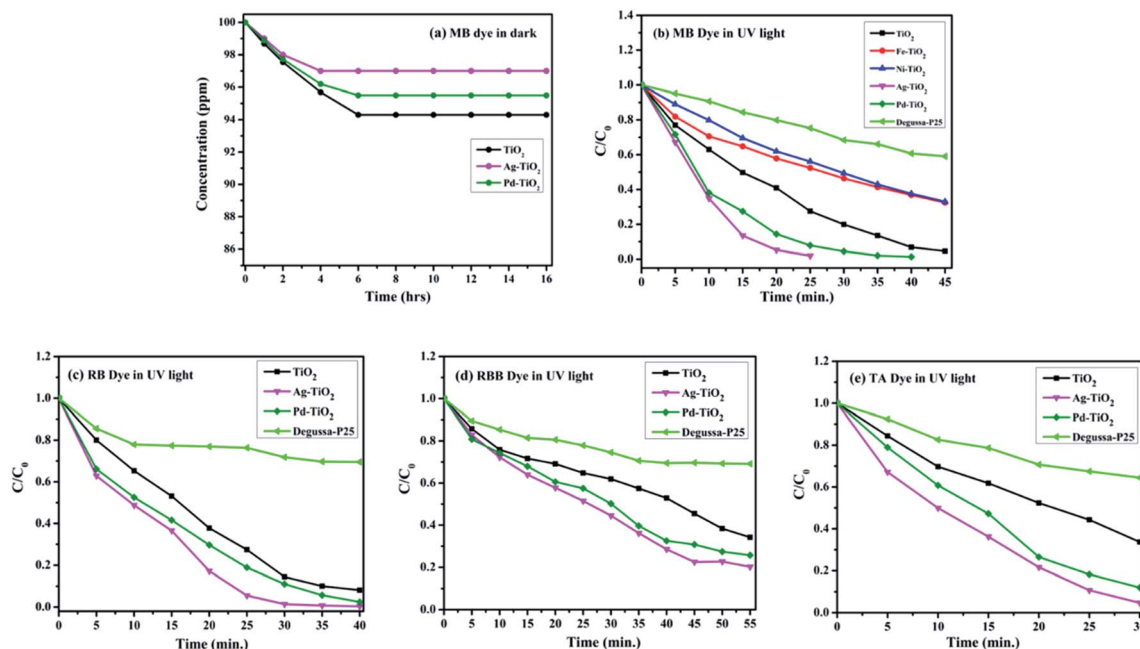


Fig. 7 (a) Degradation of MB dye using Ag^+ and Pd^{2+} doped TiO_2 and undoped TiO_2 in dark. (b) Degradation profile of MB dyes with $\text{Ti}_{1-x}\text{M}_x\text{O}_{2-\delta}$ ($\text{M} = \text{Fe}, \text{Ni}, \text{Ag}, \text{and Pd}; x = 0, 0.01$) and Degussa P25. (c)–(e) Degradation profile of RB, RBB, and TA dyes with $\text{Ti}_{1-x}\text{M}_x\text{O}_{2-\delta}$ ($\text{M} = \text{Ag}, \text{and Pd}; x = 0, 0.01$) and Degussa P25, respectively.

recombination favours the enhanced photocatalytic activity of the catalysts.

4. Photocatalytic activity

Initially, the adsorption experiment was performed by taking 100 ppm aqueous solution of MB dye over 1 kg m^{-3} of combustion synthesized metal-ion ($\text{M} = \text{Ag}$ and Pd) doped and undoped TiO_2 catalysts in the dark for 16 h to attain the

adsorption equilibrium. Fig. 7(a) clearly indicates that the adsorption saturates within 6 h and the equilibrium concentration of the MB dye in the solution of Ag^+ , Pd^{2+} doped, and undoped TiO_2 was estimated using the Beer–Lambert law and found to be 0.97, 0.95, and 0.94, respectively. Hence, this concentration was assigned as C_0 in the present study. An optimised catalyst loading of 1 kg m^{-3} and 100 ppm of initial dye concentration were maintained throughout the experiment. Depending upon the various functional groups present, four

Table 3 Initial rates and % degradation of different dyes with respect to time

Dyes	Catalysts	Initial rate of degradation ($\mu\text{mol L}^{-1} \text{min}^{-1}$)	% degradation of dye	Time (min)
Methylene blue (MB)	Ag^+ doped TiO_2	30.6	99.9%	25
	Pd^{2+} doped TiO_2	26.4	99.5%	40
	Pure TiO_2	21.6	96%	45
	Fe^{3+} doped TiO_2	16.81	70%	45
	Ni^{2+} doped TiO_2	10.8	68%	45
	Degussa P25	4.5	42%	45
Rhodamine B (RB)	Ag^+ doped TiO_2	25.5	99%	40
	Pd^{2+} doped TiO_2	23.3	97%	40
	Pure TiO_2	13.8	92%	40
	Degussa P25	9.7	30%	40
Rhodamine B base (RBB)	Ag^+ doped TiO_2	14.2	80%	55
	Pd^{2+} doped TiO_2	12.77	75%	55
	Pure TiO_2	10.9	66%	55
	Degussa P25	7.9	30%	55
Thionin acetate (TA)	Ag^+ doped TiO_2	37.8	96%	30
	Pd^{2+} doped TiO_2	23.9	88%	30
	Pure TiO_2	17.7	67%	30
	Degussa P25	8.7	36%	30



different dyes such as methylene blue (MB), rhodamine B (RB), rhodamine B base (RBB), and thionin acetate (TA) were chosen for the photocatalytic study of various catalysts in the present work. The degradation profiles of methylene blue (MB) dye using combustion synthesized pure and metal-ion ($M = \text{Fe}, \text{Ni}, \text{Ag},$ and Pd) doped TiO_2 with Degussa P25 are shown as a function of irradiation time in Fig. 7(b). An enhanced photocatalytic activity was observed in the case of Ag^+ and Pd^{2+} doped TiO_2 , whereas Fe^{3+} and Ni^{2+} doped TiO_2 shows a lower photocatalytic activity compared to undoped TiO_2 . However, all the combustion synthesized photocatalysts are still much better than Degussa P25. Since Ag^+ and Pd^{2+} doped TiO_2 shows a higher activity compared to other metal doped TiO_2 , further experiments have been carried out taking these two catalysts and their results were compared with pure- TiO_2 and Degussa P25. Fig. 7(c)–(e) show the degradation profiles of rhodamine B (RB), rhodamine B base (RBB), and thionin acetate (TA), respectively, and from the plots, it can be observed that Ag^+ and Pd^{2+} doped TiO_2 degrades the dye faster compared to TiO_2 . The initial rates and % degradation profiles of different dyes as a function of time are listed in Table 3.

5. Kinetic analysis

The effect of the initial concentration of the MB dye on the degradation rate was determined in the concentration range of 50–200 ppm with the combustion synthesized Ag^+ doped TiO_2 catalyst, and the experimental data are shown in Fig. 8(a). It can be seen from the figure that the initial concentration has a significant effect on the degradation rate and the rate of dye degradation is faster when the initial concentration is less. The kinetics of the MB dye degradation with the Ag^+ doped TiO_2 catalyst under UV irradiation was observed to follow pseudo first order reaction kinetics based on the Langmuir–Hinshelwood (L–H) model.⁵⁴ The inset of Fig. 8(a) shows that the initial rate increases with an increase in initial concentration and saturates at a higher concentration.

The generalized form of the Langmuir–Hinshelwood kinetic model for the photocatalytic degradation rate is governed by the following equation:

$$r = -\frac{dC}{dt} = \frac{k_r K_e C}{1 + K_e C} \dots \dots \dots (2)$$

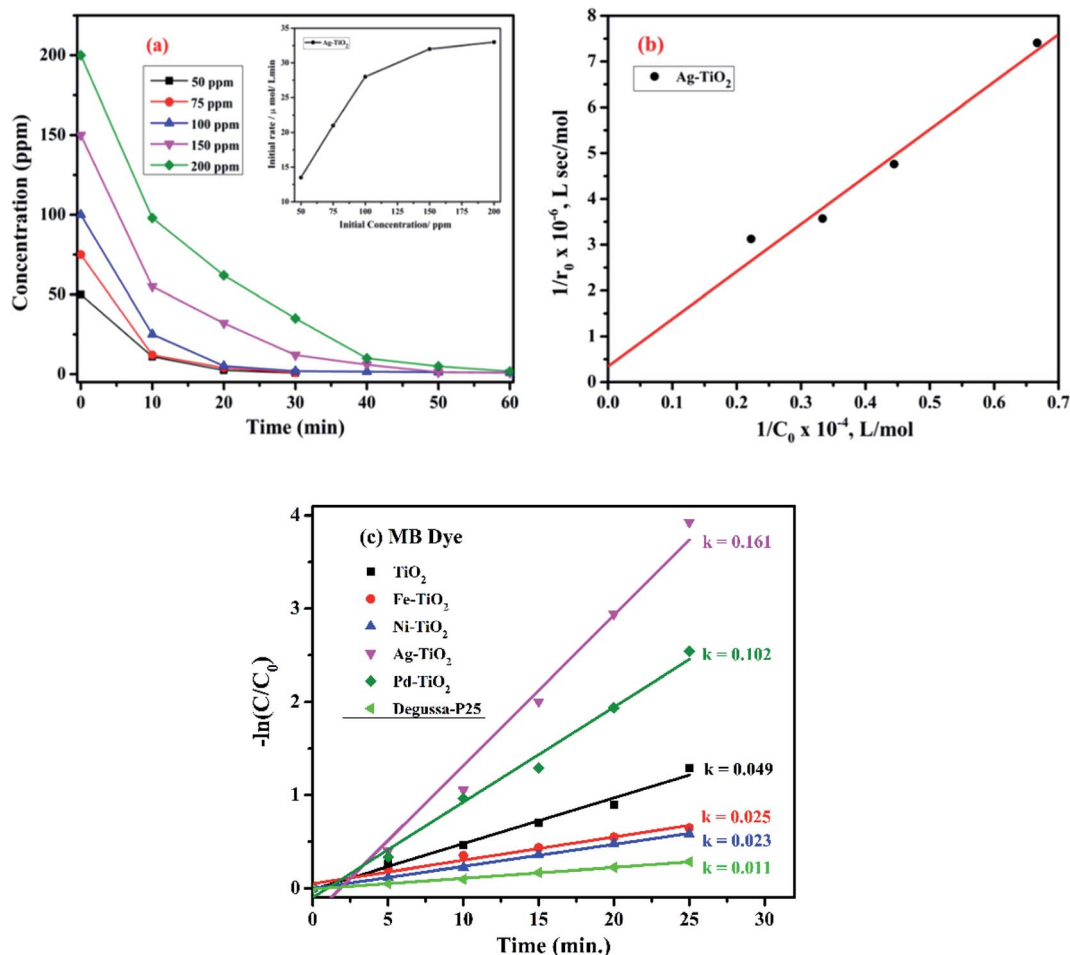


Fig. 8 (a) The effect of initial dye concentration on the degradation rate of MB with Ag-TiO_2 and (b) the Langmuir–Hinshelwood plot for MB dye with Ag-TiO_2 . (c) A comparison of the degradation kinetics of all the combustion synthesized photocatalysts using MB dye.



where k_r is the reaction rate constant and K_e is the equilibrium of adsorption constant (L-H parameter). This can be linearized for initial concentrations as:

$$\frac{1}{r_0} = \frac{1}{k_r K_e} \frac{1}{C_0} + \frac{1}{k_r} \dots \dots \dots (3)$$

where C_0 is the initial dye concentration and r_0 is the initial degradation rate. The intercept of the plot of $1/r_0$ and $1/C_0$ determines the kinetic coefficient that varies directly with the rate of degradation and the L-H parameter, K_e represents the equivalent of the adsorption coefficient. The higher value of K_e implies the blocking of the active sites of the catalyst due to strong adsorption. The higher value of k_r indicates the higher degradation rates of the dye. The rate constant and L-H parameter were calculated from Fig. 8(b) using (eqn (3)). The rate constant (k_r) is $3.211 \text{ mol L}^{-1} \text{ s}^{-1}$ and the adsorption equivalent L-H parameter (K_e) is 0.624 L mol^{-1} for Ag^+ -doped TiO_2 .

Further, the degradation profile of the MB dye shown in Fig. 7(b) has been chosen to compare the degradation kinetics of different metal-ion ($\text{M} = \text{Fe}, \text{Ni}, \text{Ag},$ and Pd) doped and undoped TiO_2 along with Degussa P25. A linear plot between $-\ln(C/C_0)$ vs. time (t) was fitted and the slope obtained is the rate constant (k) of different photocatalysts which follow pseudo-first order reaction kinetics, as shown in Fig. 8(c). The observed rate constants for $\text{Ag}^+, \text{Pd}^{2+}, \text{Fe}^{3+}, \text{Ni}^{2+}$ doped TiO_2 , and undoped TiO_2 with Degussa P25 are 0.161, 0.102, 0.025, 0.023, 0.049, and 0.011 min^{-1} , respectively. It was observed that the rate constant for Ag^+ and Pd^{2+} doped TiO_2 is 3.28 and 2.08 times higher, whereas in the case of Fe^{3+} and Ni^{2+} doped TiO_2 , it is 1.96 and 2.13 times lower than that of undoped TiO_2 , respectively.

6. Discussion

The photocatalytic activity can be correlated to the observed intensities in the PL spectra; a higher lifetime of the excited electron will give rise to a higher photo-activity of the catalyst and if the excited electron-hole recombination rates are high then they will suppress the photocatalytic performance. For the combustion synthesized samples, doping of the metal ions

create additional mid gap states within the band gap of TiO_2 that alter the recombination rate of charge carriers.⁴⁷ The energy levels of the metal ions in the TiO_2 lattice have the same band position as in their respective pristine oxides.⁵⁵ Fig. 9 shows the energy band levels of the doped metal ions in the TiO_2 lattice and they are similar to those reported by Mizushima *et al.*^{56,57} In the case of Fe^{3+} and Ni^{2+} doped TiO_2 , the metal (3d) energy levels are located just above the O^{2-} (2p) level^{32,56-58} and correspond to the band gap of 2.83 and 2.69 eV, respectively, whereas in Ag^+ and Pd^{2+} doped TiO_2 , the dopant metal (4d) level lies at 1–2 eV below the Fermi level (E_F) and their respective band gaps are 2.78 and 2.85 eV, as shown in Fig. 9. These mid-gap states which originated from metal ion doping act as centres for electron-hole trappings. When these mid-gap states are located below the CB edge, they trap the excited electrons but if these states lie above the VB edge, the photo-generated holes are trapped. Thus, the dopant ions provide more sites for trapping electrons and holes in addition to the surface defect sites. Several studies have revealed that trapping either a hole or electron is not always effective because the immobilized charge species rapidly recombines with its mobile counterpart.^{47,59,60} First row transition metal ions such as Fe^{3+} and Ni^{2+} doped TiO_2 show a lower photocatalytic activity than pure TiO_2 and do not show any change in the colour under UV light exposure, *i.e.*, these ions are not reduced to their atomic state. The intermediate state that has been created due to metal ion doping acts as a recombination centre instead of suppressing the e^-h^+ recombination and the electrons present in d-orbital quench the photogenerated holes by indirect recombination, hence increasing e^-h^+ recombination rates.³² Similarly, Ag^+ and Pd^{2+} doped titania is expected to show lower photocatalytic activity in correlation with its lower photo-luminescence intensity, which is in contrast with the actual experimental results, that is, Ag^+ and Pd^{2+} dopants show higher photocatalytic activity. The higher photocatalytic activity of Ag^+ and Pd^{2+} doped TiO_2 could be related to redox pair formation or photo-reduction of $\text{Ag}^+/\text{Pd}^{2+}$ ions through the photoelectrons generated during UV-irradiation (a phenomenon similar to photochromism in glasses). The photochromic effect in Ag^+ and Pd^{2+} doped TiO_2 compared with Degussa-P25 has been clearly

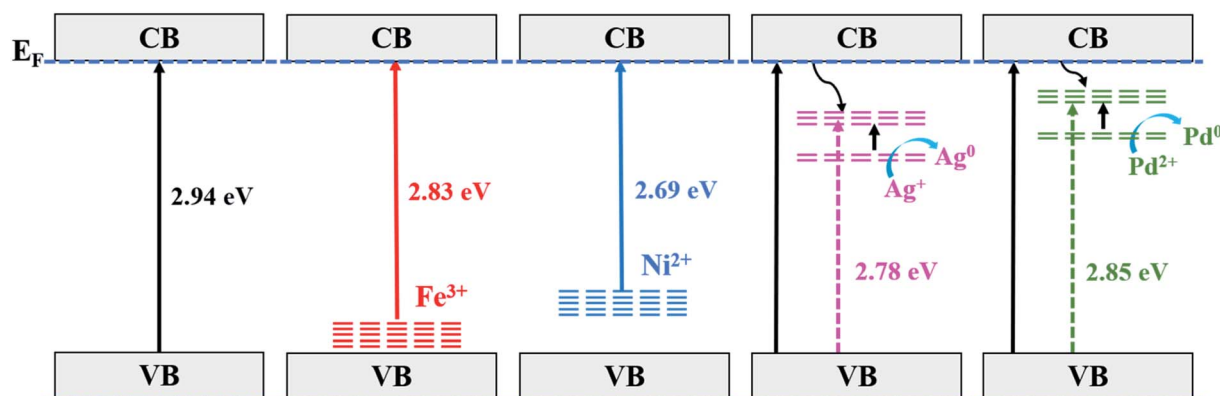


Fig. 9 A schematic representation of the different energy levels of $\text{Ti}_{1-x}\text{M}_x\text{O}_{2-\delta}$ ($\text{M} = \text{Fe}, \text{Ni}, \text{Ag},$ and $\text{Pd}; x = 0, 0.01$).




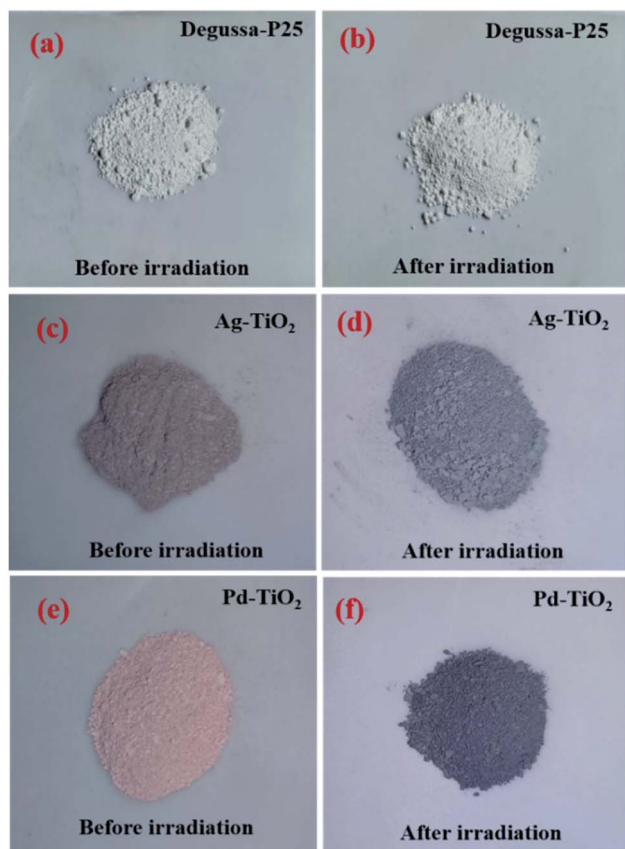


Fig. 10 (a)–(f) represent the photochromic effect in Degussa-P25, Ag⁺ doped TiO₂, and Pd²⁺ doped TiO₂, respectively.

demonstrated here through the XPS results as well as the colour changing phenomenon observed in the UV irradiated samples, as shown in Fig. 10. The sample change to the dark grey colour upon irradiation is similar to the dark colour appearance in photochromic glasses under UV-visible light, which suggests the trapping of electrons in the empty conduction band of noble metal ions. The e⁻-h⁺ pair is generated in TiO₂ via transfer of electrons from the filled O (2p) band to the empty Ti⁴⁺ bands and the excited electron is trapped in the empty conduction band of Ag⁺ and Pd²⁺ ion which can be represented as:



The photoreduction provides electron scavenging and the empty M (4d-5s) orbitals provide sites storing the excited electron as represented in Fig. 9, thus increasing the lifespan of the photogenerated holes (h⁺), which leads to the enhanced photo-oxidation/degradation of dyes.

To establish a better understanding of the photochromism that play a defining role in the development of superior photocatalysts, we have further performed the degradation

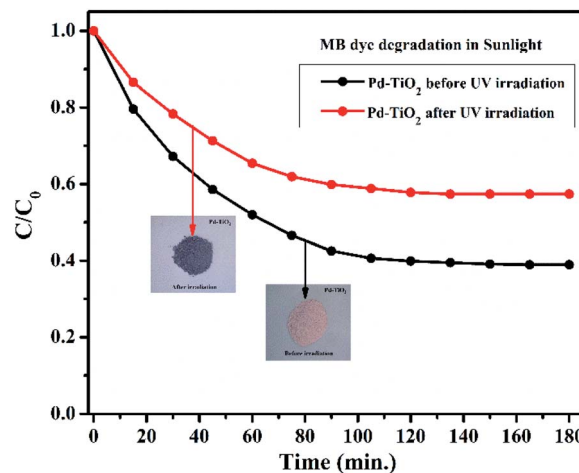


Fig. 11 Degradation of MB dye in sunlight using Pd²⁺ doped TiO₂ samples before and after UV irradiation.

experiment under sunlight. Fig. 11 represents the degradation profile of MB dye using Pd²⁺ doped TiO₂ before and after UV irradiation. It was observed that the MB dye degradation efficiency (%) of the samples before and after UV irradiation is 62% and 43% in 180 min, respectively. The presence of Pd²⁺ ion is responsible for photochromism in Pd²⁺ doped TiO₂. The concentration of Pd²⁺ ion is higher in case of before UV irradiated sample (as supported by the XPS data) which implies better degradation efficiency in comparison to the irradiated sample.

After photodegradation experiments with Ag⁺ and Pd²⁺ doped TiO₂, pXRD of the spent catalyst was recorded and no change in the XRD patterns is observed, specifically Ag and Pd metal peaks are not observed. This implies that Ag⁺ and Pd²⁺ ions upon irradiation remain in the site and segregation of Ag or Pd does not occur. In fact, the catalyst can be oxidized in air and the colour returns to the initial colour of doped TiO₂ indicating the regeneration of metal ions.

7. Conclusions

Successful synthesis of nanocrystalline Ti_{1-x}M_xO_{2-δ} (M = Pd, Ag, Fe, and Ni; x = 0, 0.01) was achieved by the solution combustion method and higher photocatalytic dye degradation activity was observed in case of Ag⁺ and Pd²⁺ doped TiO₂ photocatalysts. Upon UV irradiation, Pd²⁺ and Ag⁺ ions were reduced to their atomic state (*i.e.*, Pd²⁺ → Pd⁰ and Ag⁺ → Ag⁰) through photoelectrons, a phenomenon similar to photochromism in glasses, which was confirmed by the XPS as well as the change in colour of the compound from light brown and yellow to black, respectively. The photoreduction of the noble metal ions act as the electron scavenging step which suppress the electron-hole recombination and increase the lifespan of the holes (h⁺) required for oxidation of organic dyes. Thus, Pd²⁺ and Ag⁺ ions in TiO₂ behave differently than the first-row transition metal ions (Fe and Ni) in TiO₂ and, in turn, the Ag⁺ and Pd²⁺ doped catalysts show remarkably superior photocatalytic activity towards the oxidation of organic dyes, making them



potential candidates as heterogeneous catalysts for water pollution abatement.

Conflicts of interest

The authors declare no conflict of interest.

Acknowledgements

We thank IIT-BHU for the Seed Grants and the Department of Science and Technology (DST), Government of India for financial support.

References

- H. Zollinger, *Color chemistry: synthesis, properties and applications of organic dyes and pigments*, 2nd rev. edn, Weinheim, VCH, 1991.
- A. R. Khataee, M. N. Pons and O. Zahraa, *J. Hazard. Mater.*, 2009, **168**, 451–457.
- M. Amini and M. Ashrati, *Nanochem. Res.*, 2016, **1**, 79–86.
- M. R. Hoffmann, S. T. Martin, W. Choi and D. W. Bahnemann, *Chem. Rev.*, 1995, **95**, 69–96.
- A. G. S. Prado, L. B. Bolzon, C. P. Pedroso, A. O. Moura and L. L. Costa, *Appl. Catal., B*, 2008, **82**, 219–224.
- H. Zhang, G. Chen and D. W. Bahnemann, *J. Mater. Chem.*, 2009, **19**, 5089–5121.
- S. K. Kansal, S. Kaur and S. Singh, *Nanoscale Res. Lett.*, 2009, **4**, 709–716.
- W. Li, H. Ding, H. Ji, W. Dai, J. Guo and G. Du, *Nanomaterials*, 2018, **8**, 415.
- P. Nandi and D. Das, *Appl. Surf. Sci.*, 2019, **65**, 546–556.
- A. Fujishima, T. N. Rao and D. A. Tryk, *J. Photochem. Photobiol., C*, 2000, **1**, 1–21.
- A. Fujishima, X. Zhang and D. A. Tryk, *Surf. Sci. Rep.*, 2008, **63**, 515–582.
- J. Schneider, M. Matsuoka, M. Takeuchi, J. Zhang, Y. Horiuchi, M. Anpo and D. W. Bahnemann, *Chem. Rev.*, 2014, **11**, 9919–9986.
- X. Chen, Z. Wu, D. Liu and Z. Gao, *Nanoscale Res. Lett.*, 2017, **12**, 143.
- G. Wang, B. Huang, Z. Li, Z. Lou, Z. Wang, Y. Dai and M.-H. Whangbo, *Sci. Rep.*, 2015, **5**, 8544.
- M. R. Joya, J. B. Ortega, J. O. D. Malafatti and E. C. Paris, *ACS Omega*, 2019, **4**, 17477–17486.
- T. T. Nguyen, S.-N. Nam, J. Son and J. Oh, *Sci. Rep.*, 2019, **9**, 9349.
- Y. Zhao, C. Eley, J. Hu, J. S. Foord, L. Ye, H. He and S. C. E. Tsang, *Angew. Chem.*, 2012, **124**, 3912–3915.
- G. Nagaraju, K. Karthik and M. Shashank, *Microchem. J.*, 2019, **147**, 749–754.
- L. Korala, J. R. Germain, E. Chen, I. R. Pala, D. Li and S. L. Brock, *Inorg. Chem. Front*, 2017, **4**, 1451–1457.
- Q. Zhang, X. Li, Q. Zhao, Y. Shi, F. Zhang, B. Liu, J. Ke and L. Wang, *Appl. Surf. Sci.*, 2015, **337**, 27–32.
- V. Etacheri, M. K. Seery, S. J. Hinder and S. C. Pillai, *Adv. Funct. Mater.*, 2011, **21**, 3744–3752.
- C. Byrne, R. Fagan, S. Hinder, D. E. McCormack and S. C. Pillai, *RSC Adv.*, 2016, **6**, 95232–95238.
- K. E. Karakitsou and X. E. Verykios, *J. Phys. Chem.*, 1993, **97**, 1184–1189.
- S. Ghasemi, S. Rahimnejad, S. R. Setayesh, S. Rohani and M. R. Gholami, *J. Hazard. Mater.*, 2009, **172**, 1573–1578.
- A. Garg, A. Singh, V. K. Sangal, P. K. Bajpai and N. Garg, *New J. Chem.*, 2017, **41**, 9931–9937.
- Y. Sui, Y. Hao, G. Wen, Y. Hu, L. Wu and S. Zhong, *Appl. Surf. Sci.*, 2019, **475**, 880–886.
- S. Kim, S.-J. Hwang and W. Choi, *J. Phys. Chem. B*, 2005, **109**, 24260–24267.
- L. Körösi, S. Papp, J. Ménesi, E. Illés, V. Zöllmer, A. Richardt and I. Dékány, *Colloids Surf., A*, 2008, **319**, 136–142.
- N. T. Nolan, M. K. Seery, S. J. Hinder, L. F. Healy and S. C. Pillai, *J. Phys. Chem. C*, 2010, **114**, 13026–13034.
- R. Liu, P. Wang, X. Wang, H. Yu and J. Yu, *J. Phys. Chem. C*, 2012, **116**, 17721–17728.
- X. Pan and Y.-J. Xu, *ACS Appl. Mater. Interfaces*, 2014, **6**, 1879–1886.
- K. Nagaveni, M. S. Hegde and G. Madras, *J. Phys. Chem. B*, 2004, **108**, 20204–20212.
- K. Nagaveni, M. S. Hegde, N. Ravishankar, G. N. Subanna and G. Madras, *Langmuir*, 2004, **20**, 2900–2907.
- H. Liu, W. Yang, Y. Ma, Y. Cao, J. Yao, J. Zhang and T. Hu, *Langmuir*, 2003, **19**, 3001–3005.
- H. Choi, Y. J. Kim, R. S. Varma and D. D. Dionysiou, *Chem. Mater.*, 2006, **18**, 5377–5384.
- J.-N. Nian and H. Teng, *J. Phys. Chem. B*, 2006, **110**, 4193–4198.
- V. Chhabra, V. Pillai, B. K. Mishra, A. Morrone and D. O. Shah, *Langmuir*, 1995, **11**, 3307–3311.
- M. S. Lee, S. S. Park, G.-D. Lee, C.-S. Ju and S. S. Hong, *Catal. Today*, 2005, **101**, 283–290.
- J. Rubio, J. L. Oteo, M. Villegas and P. Duran, *J. Mater. Sci.*, 1997, **32**, 643–652.
- Z. Ding, X. Hu, P. L. Yue, G. Q. Lu and P. F. Greenfield, *Catal. Today*, 2001, **68**, 173–182.
- A. D. Paola, G. Marcì, L. Palmisano, M. Schiavello, K. Uosaki, S. Ikeda and B. Ohtan, *J. Phys. Chem. B*, 2002, **106**, 637–645.
- S. T. Aruna and K. C. Patil, *J. Mater. Synth. Process.*, 1996, **4**, 175–180.
- G. Sivalingam and G. Madras, *Appl. Catal., A*, 2004, **269**, 81–90.
- B. D. Mukri and M. S. Hegde, *J. Chem. Sci.*, 2017, **129**, 1363–1372.
- A. Gupta, U. V. Waghmare and M. S. Hegde, *Chem. Mater.*, 2010, **22**, 5184–5198.
- J. L. Coutts, P. E. Hintze, A. Meier, M. G. Shah and R. W. Devor, *et al.*, in *46th International conference on environmental systems*, Vienna, Austria, July, 2016, vol. 169.
- P. Makuła, M. Pacia and W. Macyk, *J. Phys. Chem. Lett.*, 2018, **9**, 6814–6817.
- B. Liu, X. Zhao and L. Wen, *Mater. Sci. Eng., B*, 2006, **134**, 27–31.



- 49 S. Mathew, A. K. Prasad, T. Benoy, P. P. Rakesh, M. Hari, T. M. Libish, P. Radhakrishnan, V. P. N. Nampoori and C. P. G. Vallabhan, *J. Fluoresc.*, 2012, **22**, 1563–1569.
- 50 X. Xiang, X.-Y. Shi, X.-L. Gao, F. Ji, Y.-J. Wang, C.-M. Liu and X.-T. Zu, *Chin. Phys. Lett.*, 2012, **29**, 027801.
- 51 B. Santara, P. K. Giri, K. Imakita and M. Fujii, *J. Phys. Chem. C*, 2013, **117**, 23402–23411.
- 52 T. Dhandayuthapani, R. Sivakumar and R. Ilangoan, *J. Mater. Sci.: Mater. Electron.*, 2017, **28**, 15074–15080.
- 53 V. O. Ndabankulu, S. Maddila and S. B. Jonnalagadda, *IOP Conf. Ser.: Mater. Sci. Eng.*, 2019, **668**, 012011.
- 54 R. W. Matthews, *J. Catal.*, 1988, **111**, 264–272.
- 55 S. Hüfner, *Photoelectron Spectroscopy: Principles and Applications*, Springer-Verlag Berlin Heidelberg, New York, 3rd edn, 2003.
- 56 K. Mizushima, M. Tanaka and S. Iida, *J. Phys. Soc. Jpn.*, 1972, **32**, 1519–1524.
- 57 K. Mizushima, M. Tanaka, A. Asai, S. Iida and J. B. Goodenough, *J. Phys. Chem. Solids*, 1979, **40**, 1129–1140.
- 58 S. Vasudevan, M. S. Hegde and C. N. R. Rao, *J. Solid State Chem.*, 1979, **29**, 253–257.
- 59 J. Zhou, Y. Zhang, X. S. Zhao and A. K. Ray, *Ind. Eng. Chem. Res.*, 2006, **45**, 3503–3511.
- 60 F. Huang, A. Yan and H. Zhao, *Wenbin. Cao.*, IntechOpen, 2016, pp. 31–80.

